

TEST REPORT N° 18/50785
page 1 out of 2

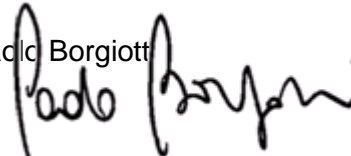

Mod.018 Rev. 2 del 12.10.2015

WEB Request Number	
Receipt Number	18/50276
Receipt date	26/11/18
Test beginning date	28/11/18
Test end date	29/11/18
Document issued on	29/11/18

FIDIVI TESSITURA VERGNANO S.p.A.
Regione Masio, 19 bis
10046 POIRINO (TO)
Phone +39 (011) 9430662
Fax +39 (011) 9461820
SAMPLE IDENTIFICATION:
A TESSUTO ART. BONDAI
THIS DOCUMENT CONTAINS THE FOLLOWING TESTS:

Code	Test	Test Method
TT0420	Abrasion Resistance of Fabrics - Martindale Machine Method - Deterioration of the fabric	UNI EN ISO 12947-2:2017

Tests results refer only to tested samples submitted by the customer.
 On each page there is the Institute dry stamp.
 Tested samples are available for 3 months.

The Analysts Prof. Paolo Borgiotti 	Technical Manager Prof. Giuseppe Bartolini 
---	--

Private document. It is not allowed to publish and spread it without lab's written authorization.

TEST REPORT N° 18/50785

page 2 out of 2

Mod.018 Rev. 2 del 12.10.2015

Beginning of Test Report

TT0420	Abrasion Resistance of Fabrics - Martindale Machine Method - Deterioration of the fabric
<i>Test methods</i>	UNI EN ISO 12947-2:2017

Rev.01 del 03/09/03

<i>Test environment</i>	Samples acclimatized for 24 hours. Normal atmosphere (Temperature: 20°C; Relative Humidity: 65%) for acclimatisation and testing conditions: UNI EN ISO 139 : 11.
<i>Testing equipment</i>	Martindale Abrasion Tester - James H.Heal & Co. LTD. Gray scale UNI EN 20105 A02 : 96
<i>Testing date</i>	29/11/2018

Test Results :

Sample identification:	TESSUTO ART. BONDAI
-------------------------------	----------------------------

<i>Pre-treatment</i>	<i>Untreated</i>
<i>Pressure</i>	<i>12 kPa</i>

Reached the deterioration (end point).

<i>Average Abrasion</i>	150.000 rubs
<i>Colour change</i>	3 / 4 ISO 105-A02
<i>Final Degradation</i>	Moderate

<i>Degradation Hystory</i>				
<i>Rubs</i>	<i>Damage</i>	<i>Effect</i>	<i>Degradation</i>	<i>Colour change ISO 105-A02</i>
20.000			None	5
50.000	Damage		Light	5
100.000	Pilling		Moderate	4
150.000	Pilling		Distinct	3/4

NB. The results reported in the tables above refer to a test analysis of the samples submitted.

End of Test Report.